

TEST REPORT

Report No. : PN:TR:1354011161

DATE : 14/09/2022



CARZSPA AUTOFRESH PRIVATE LIMITED

204, SIDDHI VINAYAK PLATINUM, OPP D.MART ON VIP ROAD, NEAR KAILASHNAGAR
SURAT-394220

IN

CONTACT PERSON : ANCKUR SAMA

THE FOLLOWING SAMPLE(S) WAS/WERE SUBMITTED AND IDENTIFIED BY/ON BEHALF OF THE CUSTOMER AS :

SAMPLE DESCRIPTION CRYSTALSHEILD GRAPHENE CERAMIC COATING G10

OEM OTHER

COUNTRY OF ORIGIN INDIA

SAMPLE RECD ON 27/08/2022

TESTING PERIOD : 12/09/2022 – 13/09/2022

TEST(S) REQUESTED PENCIL HARDNESS TEST

PENCIL HARDNESS TEST:

JIS K 5600,Part 5, Section 4:1999/As specified by client.

Test condition : Pre-conditioned at 23±2°C & 50±5% RH for 16 hrs.
Test conducted at 23±2°C & 50±5 % RH.

Pencil type : mitsubishi pencil
Pencil holding angle : 45±1°
Pencil Load : 750±10 gm
Speed : 0.5 – 1 mm/s

6B · 5B · 4B · 3B · 2B · B · HB · F · H · 2H · 3H · 4H · 5H · 6H · 7H · 8H · 9H · 10H

Softer ←————→ Harder

Requirement : 10H

Observation :


Sample No	Pencil hardness	Observation
1	10H	Sample sustained up to 10H.

Report No. : PN:TR:135401161

DATE : 14/09/2022



• Test photographs :

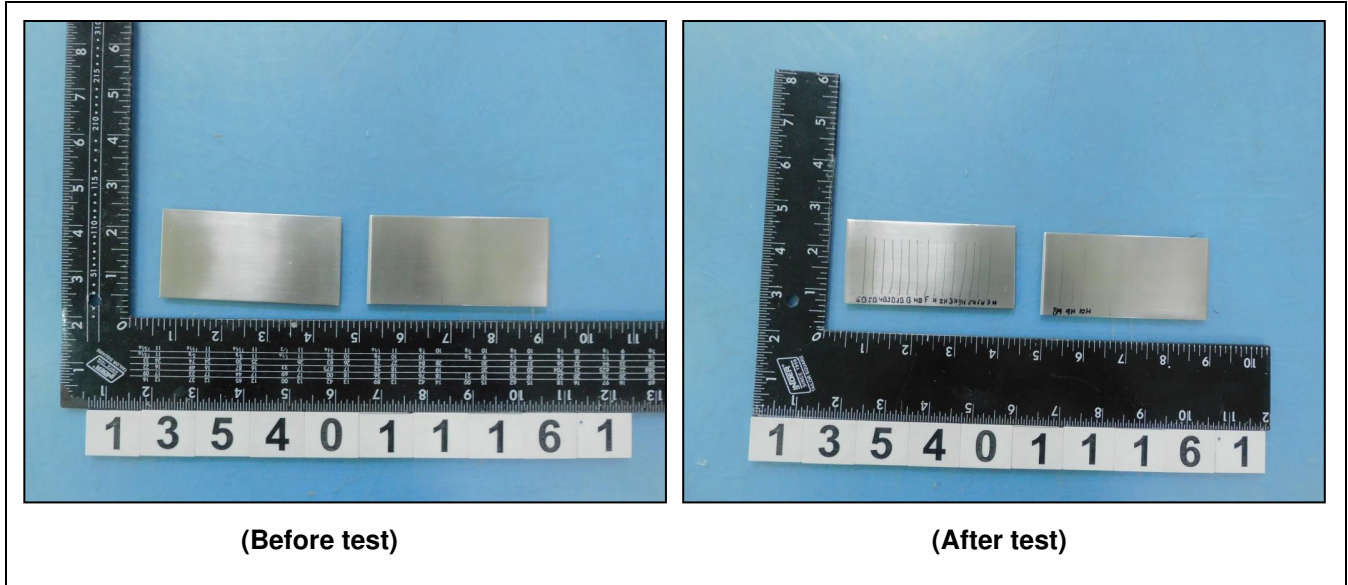

Conclusion : Tested sample meet's the requirement.

Note : Test performed as per the conditions given by the client.

***** End of Report*****

Per pro SGS India Private Ltd.

Bhushan Tambe
Executive

Email your Test Report Related Enquiries at Feedback.trp@sgs.com